

## **UWL REPOSITORY**

**repository.uwl.ac.uk**

Effect of micro TiO<sub>2</sub> on cement mortar

Shaaban, Ibrahim ORCID: <https://orcid.org/0000-0003-4051-341X>, El-Sayad, Hanaa I., El-Ghaly, Adel E. and Moussa, Sahar (2020) Effect of micro TiO<sub>2</sub> on cement mortar. *European Journal of Materials Science and Engineering*, 5 (3). pp. 58-68. ISSN 2537-4338

10.36868/ejmse.2020.05.02.058

This is the Accepted Version of the final output.

UWL repository link: <https://repository.uwl.ac.uk/id/eprint/6949/>

**Alternative formats:** If you require this document in an alternative format, please contact: [open.research@uwl.ac.uk](mailto:open.research@uwl.ac.uk)

**Copyright:** Creative Commons: Attribution-Noncommercial 4.0

Copyright and moral rights for the publications made accessible in the public portal are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

**Take down policy:** If you believe that this document breaches copyright, please contact us at [open.research@uwl.ac.uk](mailto:open.research@uwl.ac.uk) providing details, and we will remove access to the work immediately and investigate your claim.

# EFFECT OF MICRO TiO<sub>2</sub> ON CEMENT MORTAR

Ibrahim G. Shaaban<sup>a</sup>, Hanaa I. El-Sayad<sup>b</sup>, Adel E. El-Ghaly<sup>b</sup>, Sahar Moussa<sup>c</sup>

<sup>a</sup>Civil Engineering and Industrial Design Department., University of West London, UK

<sup>b</sup>Civil Engineering Department, Faculty of Engineering at Shoubra, Benha University, Egypt

<sup>c</sup>Housing and Building National Research Center, Egypt

---

## Abstract

TiO<sub>2</sub> is a primary photocatalytic ingredient. If incorporated into building materials, it can keep surfaces clean and significantly reduce smog-forming air pollutants. Many researchers have focused on the ability of Nano TiO<sub>2</sub> to reduce NO<sub>x</sub> emissions or other pollutants. However, developing countries are unable to widely utilize Nano materials due to cost and technology barriers, in spite of their great need to find means for protecting structures from pollution and improve air quality. Some studies proved that micro TiO<sub>2</sub> (commercial grade) also has photocatalytic properties. However, the effect of this inclusion on key mechanical and durability properties needs to be verified before being recommended for wide use. In this research the effect of commercial grade TiO<sub>2</sub> powder on fresh state flow, compressive strength, shrinkage, sulfate resistance and carbonation. The results indicated that TiO<sub>2</sub> decreased the workability as mortars became more sticky and dry with increased TiO<sub>2</sub> content. The compressive strength was also reduced in TiO<sub>2</sub> containing samples compared to the control samples especially at early ages. However, TiO<sub>2</sub> powder as an additive in mortar was useful in reducing carbonation due to the filler effect. No samples in the current investigation showed signs of cracking or expansive mass loss due to sulfate exposure. It is recommended that TiO<sub>2</sub> powder should be used as an additive to the mortar plaster to help in controlling the air pollution problem. However, some mix adjustment may be needed to counteract the loss in flow and strength due to the inclusion of TiO<sub>2</sub> powder.

**Keywords:** *TiO<sub>2</sub> Powder; Air pollution; Carbonation; Compressive Strength; Shrinkage; Sulfate Resistance.*

---

## Introduction

TiO<sub>2</sub> is a primary photocatalytic ingredient that can significantly reduce smog-forming air pollutants in urban and metropolitan areas (pollution abatement) [1-3]. The number of TiO<sub>2</sub> patents is continually growing and currently include materials in concrete tiles, concrete paving, white cement (architectural concrete), applications on building surfaces, as well as environment-friendly cement (TioCem) [4-6].

Heterogeneous photo catalysis was first discovered by Fujishima and Honda in the 1970's. It is a process involving a catalyst that absorbs UV energy from the sun and oxidizes or decomposes organic matters in either the atmosphere or aquatic environments [7]. In addition to photocatalytic properties, TiO<sub>2</sub> is chemically and biologically inert, non-toxic, which makes it an accessible material for general applications. The study of the usage of TiO<sub>2</sub> in construction materials as a photocatalytic material initiated in the early 1990s [8].

Previous investigations concentrated on the photocatalytic properties of Nano TiO<sub>2</sub> [9-10], as well as TiO<sub>2</sub> containing cement-based materials [8, 11]. The majority of this effort has been on characterizing and enhancing the photocatalytic efficiency.

Some time ago it was suggested [12] that there is potential for using commercial TiO<sub>2</sub> as a in the surface layer of exterior slabs to reduce air pollution. More recently a number of investigations have confirmed that commercial grade TiO<sub>2</sub> powder has photocatalytic properties. Hanson [13] studied different TiO<sub>2</sub> types from different manufactures to help identify which crystalline type, particle size, purity, and quantity of TiO<sub>2</sub> would be the most appropriate product to add to the concrete matrix to create a photocatalytic, NO<sub>x</sub> reducing concrete surface. TiO<sub>2</sub> powders used in that study were either commercially available as photocatalytic grade or

other samples not manufactured for photocatalytic properties. It was concluded that only some  $\text{TiO}_2$  powder types in the anatase phase had the ability to significantly decrease  $\text{NO}_x$  pollutant concentrations. The effective anatase phases were approximately  $1.0 \mu\text{m}$  in average size and had purities between 83 and 97%. The less effective anatase phase had a smaller particle size and greater than 98% purity. It was noted that the efficiency was greater if  $\text{TiO}_2$  was available near the surface of the material's cross section, so that it can be activated by solar radiation. Hanson's [13] work showed that coarser and less pure anatase  $\text{TiO}_2$  is an effective photocatalyst, and the optimum dose in the mix was below 9% by weight of cement. Gatto [14] used micro-sized  $\text{TiO}_2$  powders for the photo-degradation of  $\text{NO}_x$  and toluene pollutants. It was found that all micrometric  $\text{TiO}_2$  powders, even though they are sold as not photocatalytic materials, showed good results. It was recommended that micro  $\text{TiO}_2$  powders should be used rather than Nano  $\text{TiO}_2$  in order to reduce health problems associated with difficult recovery and consequently health hazards due to inhalation of Nano particles.

## Research Significance

Although the effects of Nano  $\text{TiO}_2$  on various mortar and concrete properties have been thoroughly investigated [e.g. 15-18], the authors could not cite any studies on the effect of commercial grade  $\text{TiO}_2$  on the engineering properties of mortars.

The main purpose of this research was to investigate the properties of mortars containing commercial grade  $\text{TiO}_2$ . This is essential before the use this powder is recommended on a regular basis. The powder was utilized as an additive in small quantities not exceeding 9% by weight of cement. The experimental program has been developed to investigate the following:

1. The effect of  $\text{TiO}_2$  content on flow of mortars in the fresh state.
2. The effect of  $\text{TiO}_2$  content on compressive strength of mortars.
3. The carbonation potential of  $\text{TiO}_2$  containing samples compared to samples without it.
4. The length change of mortars with and without  $\text{TiO}_2$  as an indication of shrinkage.
5. The behavior of mortars with and without  $\text{TiO}_2$  exposed to Sodium Sulfate Solution.

## Experimental Program Materials

Ordinary Portland Cement (OPC) used throughout the test program was Suez Cement (CEM I 42.5 N). OPC surface area and specific gravity were  $3500 \text{ cm}^2/\text{g}$  and  $3150 \text{ kg}/\text{m}^3$  respectively as specified by cement testing laboratory in Housing and Building Research Center and conforming to the requirements of ESS 4756-1/2013 [19]. The chemical composition of the cement is shown in Table 1. Titanium Dioxide ( $\text{TiO}_2$ ) was supplied from El Naser Pharmaceuticals Chemicals.  $\text{TiO}_2$  was in solid state (powder), having slight odor and white color as shown in Fig. 1.  $\text{TiO}_2$  purity was 98%. The physical properties of  $\text{TiO}_2$  as obtained from the material manufacturer data sheet are illustrated in Table 2. Fig. 2 for X-Ray Diffraction analysis of  $\text{TiO}_2$  reveals that it is mainly anatase phase. The particle size distribution of  $\text{TiO}_2$  powder was measured by HORIBA Laser Scattering Particle Size Distribution Analyzer Partica LA-950. Fig. 3 and Table 3 show the particle size distribution and values for  $\text{TiO}_2$  powder. Natural sand locally sourced from Giza desert was used as fine aggregate with average size ( $600 \mu\text{m}$ - $1.18 \text{ mm}$ ). The water used was the potable tap water.

# EFFECT OF MICRO TiO<sub>2</sub> ON CEMENT MORTAR

**Table 1.** Chemical composition of portland cement


Component	SiO <sub>2</sub>	Al <sub>2</sub> O <sub>3</sub>	Fe <sub>2</sub> O <sub>3</sub>	CaO	MgO	SO <sub>3</sub>	Na <sub>2</sub> O	K <sub>2</sub> O	L.O.I
Content (%)	20.39	5.6	3.43	63.07	2.91	0.7	0.38	0.35	2.06




**Fig. 1.** Titanium dioxide powder physical appearance

**Table 2.** Physical properties of TiO<sub>2</sub>

Name	TiO <sub>2</sub> powder
Appearance	white
Particle size	0.2912 - 0.6746 $\mu$ m
Purity	98 %
L.O.I	0.13 %

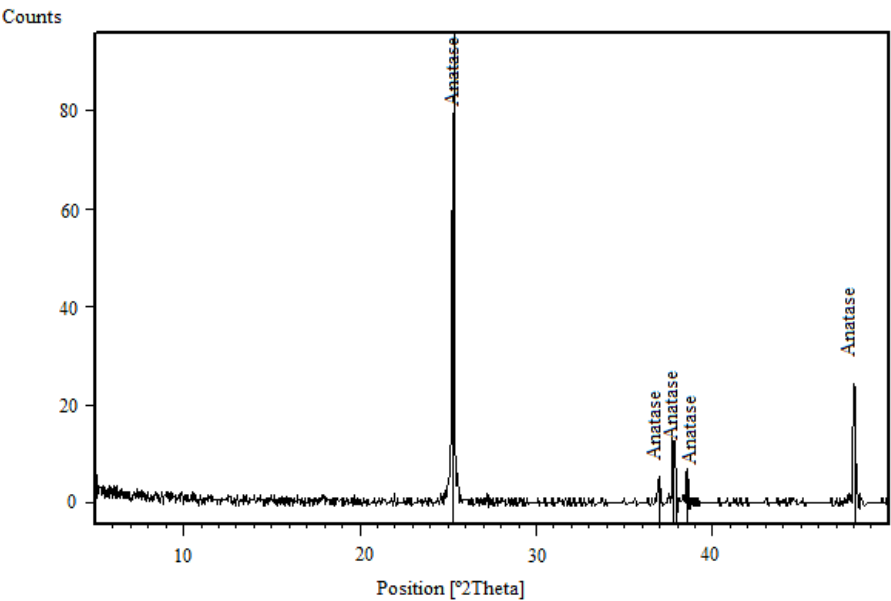

**Fig. 2.** X-Ray diffraction analysis of TiO<sub>2</sub>

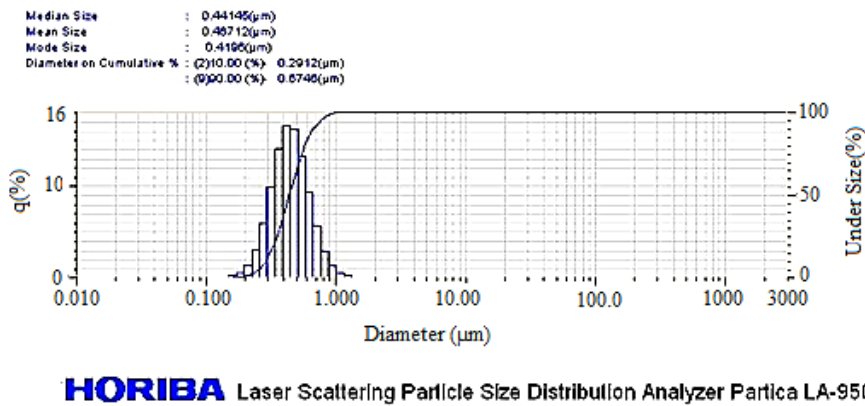

**Fig. 3.** Particle size distribution of  $\text{TiO}_2$  powder

**Table 3.** Particle size distribution values of  $\text{TiO}_2$  powder

No.	Diameter [ $\mu\text{m}$ ]	q[%]	Under Size[%]
20	0.160	0.000	0.000
21	0.172	0.167	0.167
22	0.197	0.510	0.677
23	0.226	1.302	1.979
24	0.269	2.936	4.916
25	0.296	6.816	10.731
26	0.339	9.841	20.672
27	0.389	13.959	34.631
28	0.445	16.457	50.988

No.	Diameter [ $\mu\text{m}$ ]	q[%]	Under Size[%]
29	0.510	16.138	67.126
30	0.584	13.267	80.393
31	0.669	9.263	89.646
32	0.766	6.538	95.184
33	0.877	2.867	98.051
34	1.005	1.286	99.337
35	1.151	0.498	99.835
36	1.318	0.165	100.000

## Mixes and Sample Preparation Procedure

A total of four mixes were prepared in the laboratory. The control mix was prepared from natural sand, cement and water. The water to binder ratio for all mortars mixes was set at 0.50. The cement content of all mixes was  $350 \text{ kg/m}^3$ . The cement to sand ratio for all mixes was set at 1:3. Other mixes were prepared with different contents of  $\text{TiO}_2$  particles as an additive at 3%, 6% and 9% by weight of cement. A small electrical mixer was used for mixing mortars. The samples were cubes  $50\text{mm} \times 50\text{mm} \times 50\text{mm}$  and prisms  $25\text{mm} \times 25\text{mm} \times 285 \text{ mm}$ . The specimens were cast and compacted in two layers using a plastic compacting bar, where each layer was compacted 25 times. Then the molds were placed on compacting table and vibrated for about 15 seconds. The molds were immediately covered with plastic sheet to avoid moisture loss, and were kept at room temperature ( $23 \pm 2^\circ\text{C}$ ) for 24 hours. The specimens were then de-moulded and were kept in water for seven days for moist curing.

# EFFECT OF MICRO TiO<sub>2</sub> ON CEMENT MORTAR

## Testing Procedures

The tests performed were Flow table, Compressive strength, change in length, and sulfate attack in accordance with ASTM C 1437 – 07 [20]; ASTM C109 / C109M - 16a [21]; ASTM C157 / C157M – 17 [22]; ASTM C1012 / C1012M – 15 [23], respectively. The details of the prepared cubes, prisms and tests performed are presented in Table 4.

**Table 4.** Details of experimental program

Fresh State								
Tio <sub>2</sub> % added	Control	3%	6%	9%	Control	3%	6%	9%
Flow Test	Repeat test 3 times for each mix, flow= average of 3 readings							
Hardened State								
Compressive Strength test	Specimens in Air							
	Control	3%	6%	9%				
	Testing (3) cubes for each at 28, 56, 90 days							
Carbonation Resistance					Specimens in CO2 Chamber			
					Control	3%	6%	9%
					Testing (3) cubes for each at 28, 56, 90 days			
Shrinkage Test	Testing (5) prisms for each at 28, 56, 90 days							
Sulfate Attack					Specimens in Sulfate Solution			
					Control	3%	6%	9%
					Testing (5) prisms for each at 28, 56, 90 days			

## Results and Discussion

### Flow Table Test

Fig. 4 shows the flow table test results. The mortar consistency decreased as TiO<sub>2</sub> percentage increased. The reason may be that TiO<sub>2</sub> is hydrophilic material (the capability of TiO<sub>2</sub> to absorb the mixing water). Therefore, the increase in TiO<sub>2</sub> content in the mortar lead to a reduction in observed flow diameter [24].The flow is defined as the percentage increase in the average diameter of the spread mortar (D in cm), over the original diameter of the base (10 cm). The percentage expresses the degree of mortar consistency.

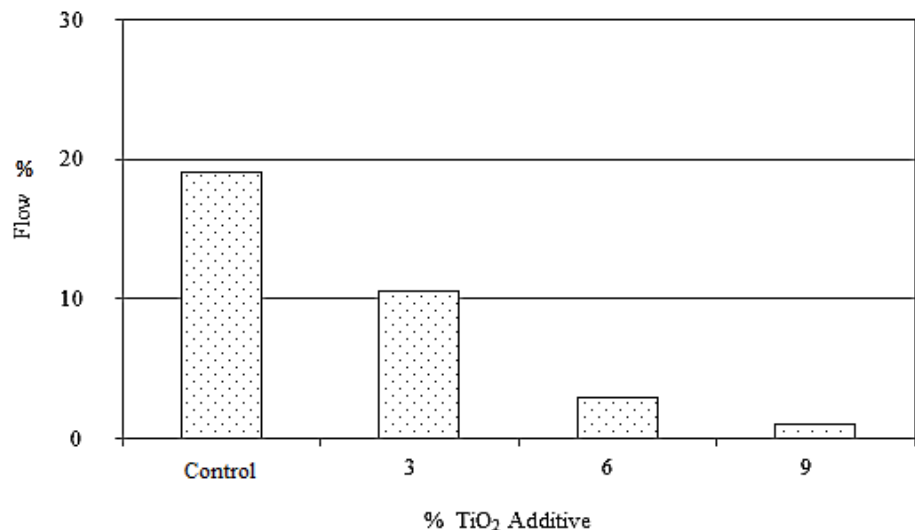


Fig. 4. Flow table test results of mortars

### Compressive Strength Test

Fig. 5 shows the average compressive strength of all samples at the ages of 28, 56 and 90 days. The compressive strength decreased by increasing the amount of TiO<sub>2</sub> except for 6% TiO<sub>2</sub> mortars. In fact there is some improvement in compressive strength of 6% TiO<sub>2</sub> at the later age of 90 days. For mixes with 6% TiO<sub>2</sub>, strength was better than 3% and 9% TiO<sub>2</sub>. By increasing TiO<sub>2</sub> to 9%, the compressive strength was decreased by 39.9%, 30.5%, and 6.5% at ages 28, 56, and 90 days respectively compared to the control mix. This may be attributed to the possibility that the TiO<sub>2</sub> content in mixture was higher than the amount required to combine with the liberated lime during the process of hydration thus causing a deficiency in strength [24]. The increase in TiO<sub>2</sub> does not contribute to strength. Also, it may be due to the defects generated in dispersion of TiO<sub>2</sub> that causes weak zones [24]. Fig. 6 shows the ratio of strengths between TiO<sub>2</sub> mortar specimen and control specimen. It is clear that at later ages the difference in strength between samples with and without TiO<sub>2</sub> was small.


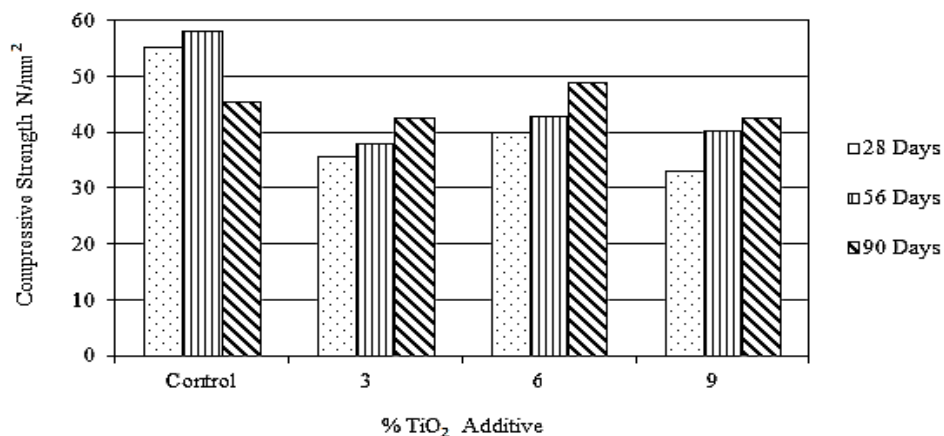


Fig. 5. Compressive strength results of cubes

## EFFECT OF MICRO TiO<sub>2</sub> ON CEMENT MORTAR

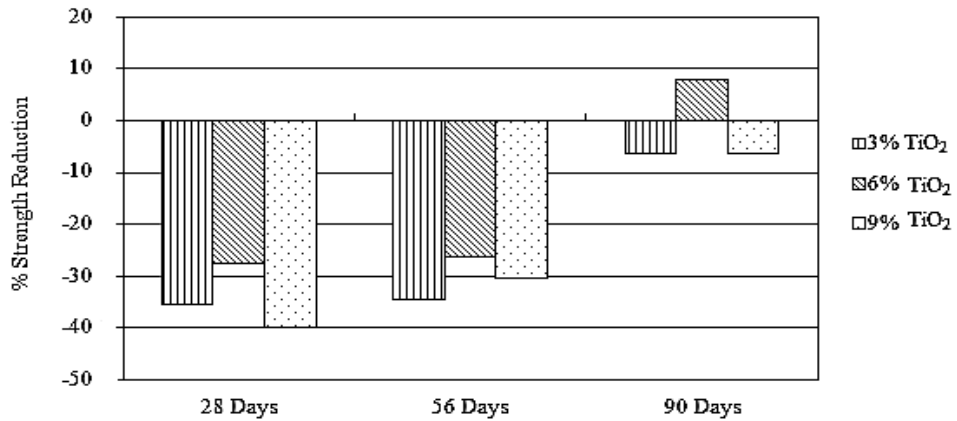

**Fig. 6.** Ratio of strengths between TiO<sub>2</sub> and control mortar at various ages

In a research that utilized Nano TiO<sub>2</sub> as a partial cement replacement it was reported that the compressive strength increased with higher TiO<sub>2</sub> Nanoparticle replacement at lower water-to-solids ratio ( $w/s = 0.40$ ) and strength is not compromised by up to 10% TiO<sub>2</sub> replacement at higher  $w/s = 0.60$  [25]. Similarly, mortar samples with 1, 3 or 5% nano-TiO<sub>2</sub> exhibited improved strength up to 28 days of curing compared to ordinary samples [26]. However, the Nano particles were dispersed a water reducer before mixing and naturally the Nano particles affect the microstructure in a more profound way compared to micro particles and this perhaps caused the observed enhanced strength.

### Carbonation Depth

Fig. 7 illustrates the observations upon the application of Phenolphthalein Indicator to determine the effect of TiO<sub>2</sub> powder on the carbonation of mortar cubes exposed to CO<sub>2</sub> gas for 28, 56, and 90 days. It can be seen that the carbonation depth decreased as TiO<sub>2</sub> percentage increased. The carbonation depth of control samples was increased with long exposure to CO<sub>2</sub> gas. However, the presence of TiO<sub>2</sub> significantly reduced CO<sub>2</sub> depth especially at later ages.

The improvement in carbonation resistance with the inclusion of TiO<sub>2</sub> can be observed clearly after 28 days of curing. Similarly SEM test results had previously concluded that the incorporation of nano-TiO<sub>2</sub> particles refines the microstructure and improves the carbonation resistance [27].

In another investigation, TiO<sub>2</sub> partially replaced either fine aggregate or cement, it was reported that samples with TiO<sub>2</sub> exhibited slightly higher carbonation depths after 13 weeks of CO<sub>2</sub> exposure [28]. The depths were higher with high W/B ratios and increased replacement levels leading to lower alkalinity to start with.

### Shrinkage Test

Fig. 8 and Fig. 9 show the average of change of length for test prisms kept in laboratory air for 90 days. Five samples were tested for each mix. The change in length was determined as follows:


$$\% \text{ Change in Length} = (L_0 - L_1) / L_0 \% \quad (1)$$

Where:

$L_0$  = Length of specimen after water curing.

$L_1$  = Length of specimen at a specified test age



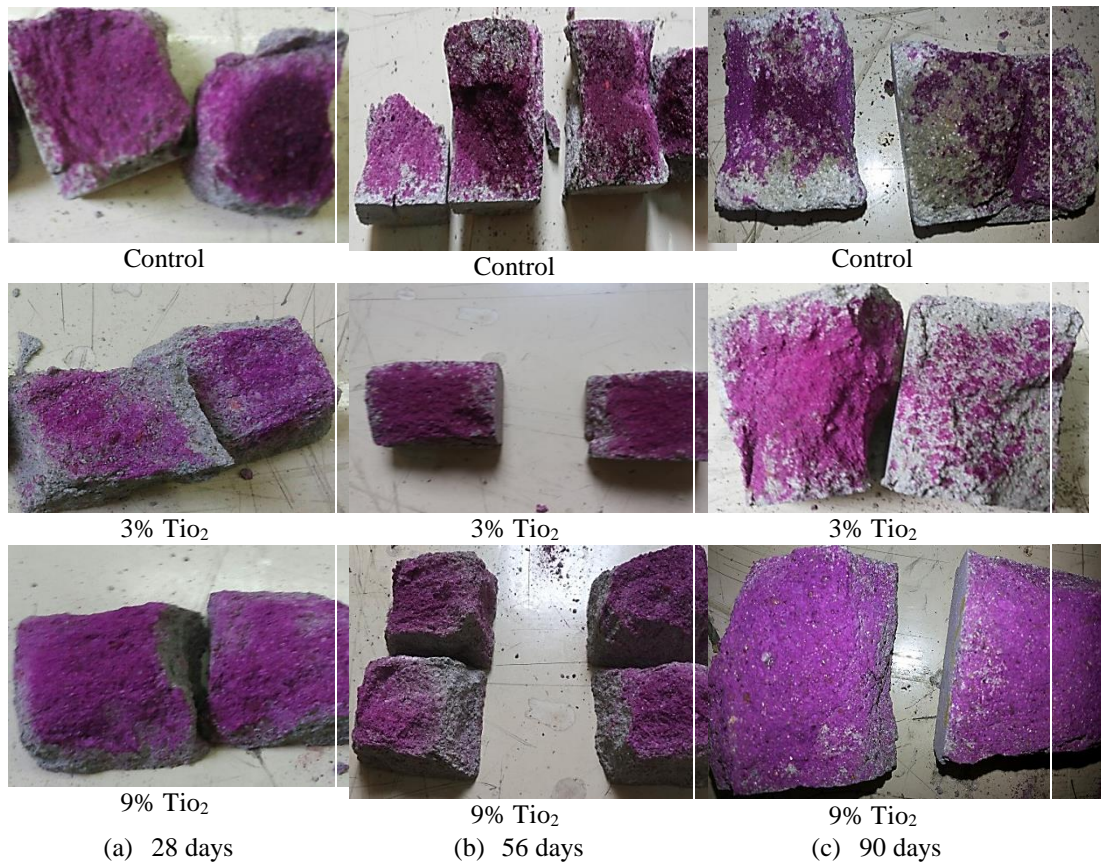

**Fig. 7.** Carbonation depth test at different ages  
(a) 28 days (b) 56 days (c) 90 days

It can be seen that the percentage change in lengths lightly increased with increasing  $\text{TiO}_2$  content at all ages. Naturally, the shrinkage increased with time. Similarly, in an investigation using Nano  $\text{TiO}_2$  in concrete it was reported that after 28 days, the drying shrinkage rate of the concrete with 1% nano- $\text{TiO}_2$  was 1.6 times that of ordinary concrete [29]. However, mortar samples with 1, 3 or 5% nano- $\text{TiO}_2$  exhibited less water loss during shrinkage measurements compared to those without nano- $\text{TiO}_2$  [26]. It should be noted that the Nano particles act in a different manner compared to the micro particles and this perhaps caused the reduction in shrinkage. Fig. 9 indicates that the  $\text{TiO}_2$  percentage had a small effect on length change values as all samples with  $\text{TiO}_2$  exhibited similar shrinkage at each testing age.

## EFFECT OF MICRO TiO<sub>2</sub> ON CEMENT MORTAR

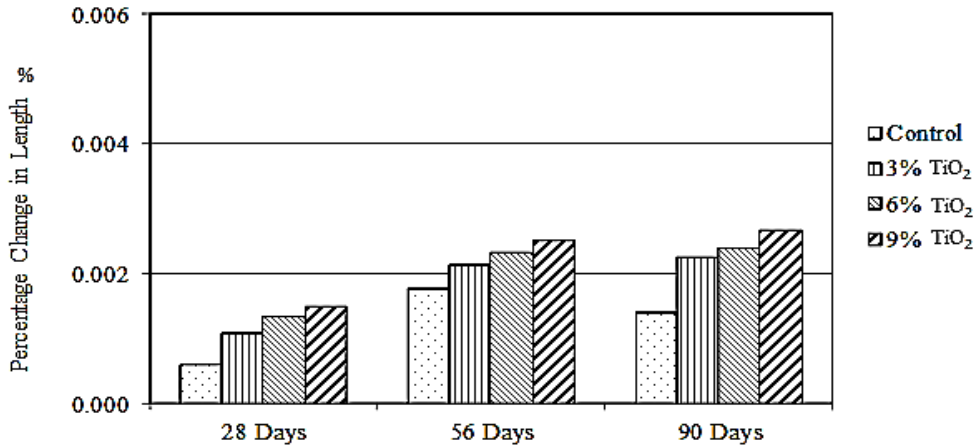


Fig. 8. Percentage change in length of prisms kept in air

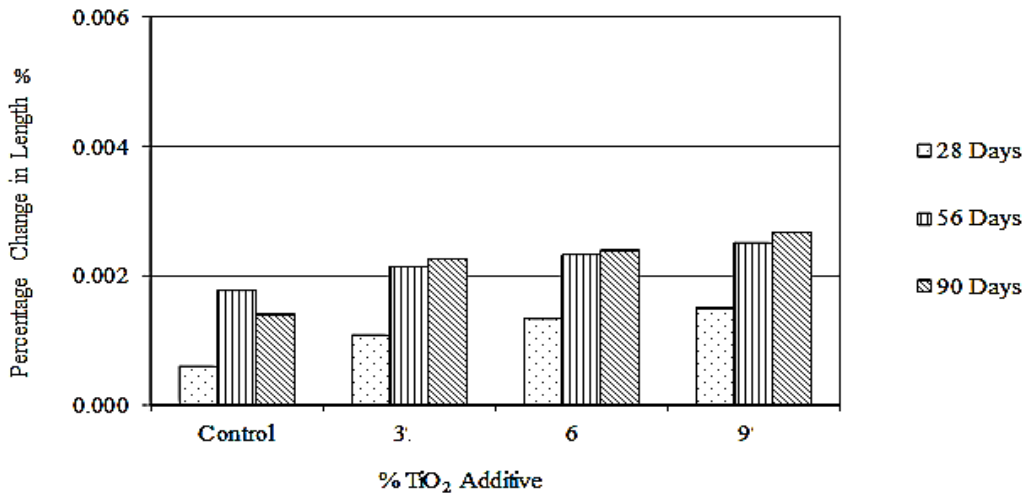



Fig. 9. Percentage Change in length of prisms kept in air at different ages

### Sulfate Attack Test

Fig. 10 shows the prism samples immersed in sulfate solution in glass container. The top of the container was glass plate then sealed to prevent evaporation. Fig. 11 shows the average of change of length test prisms during 90 days sulfate solution exposure. Five samples were tested from each mix. It can be observed that the expansion of mortar prisms was decreased by increasing TiO<sub>2</sub> percentage at all ages except for 9% TiO<sub>2</sub>. The 9% TiO<sub>2</sub> mortar prisms were shrinking in sulfate solution. Table 5 shows the percentage mass loss of prisms kept in sulfate solution. It can be seen that the shrinkage of 9% TiO<sub>2</sub> samples was not due to mass loss. In fact no samples exhibited cracking in the current investigation. Mass loss values were smaller with higher percentage of TiO<sub>2</sub>.



**Fig. 10.** Setup for sulfate attack test

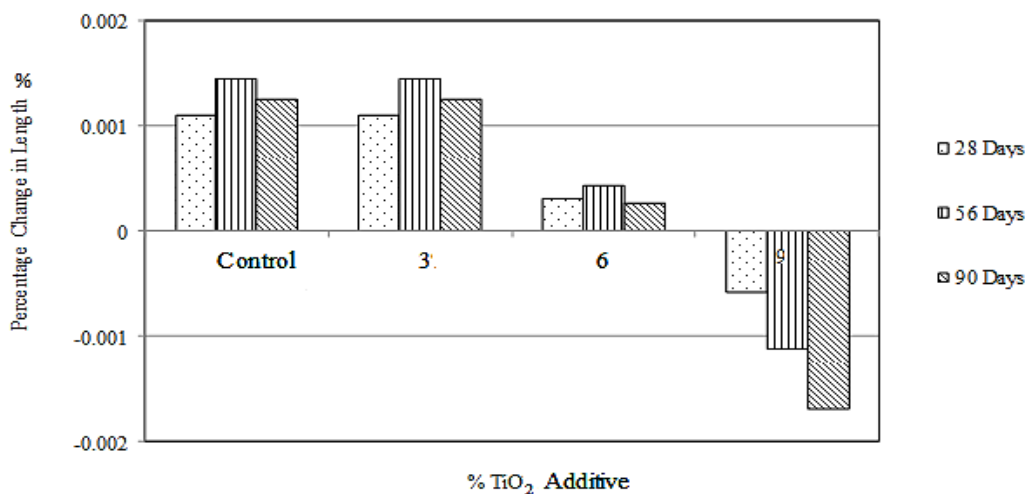

**Fig. 11.** Percentage Change in length of prism kept in sulfate solution

**Table 5.** Percentage mass loss of prisms kept in sulfate solution

Mix	28 Days	56 Days	90 Days
Average for Control	0.50%	0.86%	0.69%
Average for 3% TiO <sub>2</sub>	0.50%	0.86%	0.69%
Average for 6% TiO <sub>2</sub>	0.47%	0.25%	0.08%
Average for 9% TiO <sub>2</sub>	0.40%	0.10%	0.06%

It has been reported that the use of TiO<sub>2</sub> Nano particles improves the resistance to water permeability of concrete when it is mixed in cement pastes [30, 31]. This improved water ingress resistance should contribute to better resistance to all chemical attack including sulfate attack.

In another publication, samples of 5%, 10%, and 15% Nano TiO<sub>2</sub> mortar prisms were immersed partially in 15% Na<sub>2</sub>SO<sub>4</sub> solution developed heavy efflorescence within several days

## EFFECT OF MICRO TiO<sub>2</sub> ON CEMENT MORTAR

---

after the start of the experiment, with white deposits covering whole sample surfaces. However, no cracking was observed on the sample surfaces. Therefore, the aesthetics of the samples were negatively affected, but the soundness was not impaired [32].

The effect of TiO<sub>2</sub>Nano particles on Fly Ash concrete properties was investigated. The results confirmed higher resistance to sulfate attack due to addition of Nano particles to Fly Ash concrete. In addition, Fly Ash-nano titanium dioxide specimens showed lesser weight loss compared to Fly Ash concrete without Nano TiO<sub>2</sub> [33].

### Conclusions

The addition of TiO<sub>2</sub> reduces the flow of the mortar mixes measured in accordance with ASTM: C 1437– 07.

The compressive strength of mortars was tested in accordance with ASTM C109/C109M-16a and was reduced with inclusion of TiO<sub>2</sub>; however, this decrease in strengths was less noticeable at later ages.

The samples kept in laboratory air all exhibited comparable shrinkage regardless of the TiO<sub>2</sub> content. However, shrinkage of these mortars was slightly higher than the control mortar.

By storing the samples in the proposed built CO<sub>2</sub> chamber for up to 90 days, the samples containing TiO<sub>2</sub> showed small or no carbonation depth. However carbonation occurred in the control samples.

Samples with 3% TiO<sub>2</sub> exhibited similar behavior to the control samples when exposed to sulfate for up to 90 days. The test was conducted in accordance with ASTM C1012-04. Samples with higher TiO<sub>2</sub> exhibited better performance compared to the control samples without TiO<sub>2</sub>. No samples in the current investigation showed signs of cracking or expansive mass loss due to sulfate exposure.

The properties of samples containing micro TiO<sub>2</sub> used in this investigation may show similar trends to the properties reported in the literature for Nano TiO<sub>2</sub>. However, it should be remembered that the mechanism of action of each type of particle at the microstructure level is different and the comparison was quoted here to draw the attention to the expected behavior in service for both types of materials.

The current consensus in the literature [34] points towards the beneficial effect of TiO<sub>2</sub> additions to cement composites as the product has self-cleaning, self-disinfecting, and depolluting effects.

It is recommended that TiO<sub>2</sub> should be used as an additive to the mortar plaster. However, the mortar with TiO<sub>2</sub> would need to be optimized for consistency and compressive strength to be used effectively.

### References:

- [1] D. Shafaei, S.Yang, L. Berlouis, J. Minto, *Multiscale pore structure analysis of nano titanium dioxide cement mortar composite*, **Material Today Communications**, 22, 2020, pp.100779–100788. <https://doi.org/10.1016/j.mtcomm.2019.100779>
- [2] C.S. Poon, and E. Cheung, *NO Removal Efficiency of Photocatalytic Paving Blocks Prepared with Recycled Materials*, **Construction and Building Materials**, 21(8), 2007, pp. 1746-1753.
- [3] M.M. Hassan, L.N. Mohammad, S.B. Cooper, H. Dylla, *Evaluation of Nano-Titanium Dioxide Additive on Asphalt Binder Aging Properties*, **Journal of the Transportation Research Board**, 2207, Transportation Research Board of the National Academies, Washington, D.C., 2011, pp. 11–15. DOI: 10.3141/2207-02.

- [4] TX Active®, Lehigh Hanson, Inc., <https://www.lehighhanson.com/products/cement/tx-active> (Accessed March 2020).
- [5] Yoshihiko, M. K. Kiyoshi, T. Hideo, O. Hiroshi, and Y. Yutaka, *NO<sub>x</sub> Removing Pavement Structure*, **US Patent Office**, Patent No. 6454489, 2002.
- [6] TioCem®, Heidelberg Cement, <https://www.heidelbergcement.de/de/tiocem-en> (Accessed March 2020).
- [7] A. Fujishima, K. Honda, *Electrochemical Photolysis of Water at a Semiconductor Electrode*, **Nature** **238**, 1972, pp. 37-38.
- [8] M. V. Diamanti, M. Peddeferri, *Photocatalytic performance of mortars with nanoparticles exposed to the urban environment*, **Nanotechnology in Eco-efficient Construction (Second Edition) Materials, Processes and Applications**, Wood head Publishing Series in Civil and Structural Engineering, 2019, pp. 527-555, <https://doi.org/10.1016/B978-0-108-102641-0.00022-0>
- [9] A. Fujishima, X.T. Zhang, D.A. Tryk, *TiO<sub>2</sub> Photocatalysis and Related Surface Phenomena*. **Surface Science Reports**, 63(12), 2008, pp. 515-582.
- [10] O. Carp, C.L. Huisman, A. Reller, *Photoinduced Reactivity of Titanium Dioxide*, **Progress in Solid State Chemistry**, 32(1-2), 2004, pp. 33-177.
- [11] T. Maggos, A. Plassais, J.G. Bartzis, Ch. Vasilakos, N. Moussiopoulos, L. Bonafous, *Photocatalytic Degradation of NO<sub>x</sub> in a Pilot Street Canyon Configuration Using TiO<sub>2</sub>-mortar Panels*, **Environmental Monitoring and Assessment**, 136(1-3), 2008, pp. 35-44.
- [12] D.H. Chen, K-Y. Li, R. Yuan, *Photocatalytic Coating on Road Pavements/Structures for NO<sub>x</sub> Abatement*, **Texas Air Research Center, Lamar University, Beaumont, Texas**. Available at: <http://citeseerx.ist.psu.edu/viewdoc/download?doi=10.1.1.604.5945&rep=rep1&type=pdf>
- [13] S. Hanson, *Evaluation of Concrete Containing Photocatalytic Titanium Dioxide*. **PhD Thesis, Department of Civil and Environmental Engineering, University of Utah, USA**, 2014.
- [14] S. Gatto, *Photocatalytic Activity Assessment of Micro-sized TiO<sub>2</sub> used as Powders and as Starting Material for Porcelain Gres Tiles Production*, **PhD Thesis, Department of Chemistry, University of Milano, Italy**, 2014.
- [15] A. Nazari, S. Riahi, *The effect of TiO<sub>2</sub> Nanoparticles on Physical, Thermal and Mechanical Properties of Concrete Using Granulated Blast Furnace Slag as Binder*, **Materials Science and Engineering A**, 528(4-5), 2011, pp. 2085-2092.
- [16] B. Ma, H. Li, X. Li, J. Mei, Y. Lv, *Influence of Nano-TiO<sub>2</sub> on Physical and Hydration Characteristics of Fly Ash–Cement Systems*, **Construction and Building Materials**, 122, 2016, pp. 242–253.
- [17] J. Chen, S. Kou, C. Poon, *Hydration and Properties of Nano-TiO<sub>2</sub> Blended Cement Composites*. **Cement and Concrete Composites**, 34(5), 2012, pp. 642–649.
- [18] S.N. Zailan, N. Mahmed, M.A.A Abdullah, A.V. Sandu, N.F. Shahedan, *Review on Characterization and Mechanical Performance of Self-cleaning Concrete*. **MATEC Web of Conferences**, 97(01022), 2017, pp.1-7.
- [19] Egyptian Standard Specification 4756-1, *Cement Part (1) Composition, Specifications and Conformity Criteria for Common Cements*, 2013.
- [20] ASTM C 1437–07, *Standard Test Method for Flow of Hydraulic Cement Mortar*, 2007.

## EFFECT OF MICRO TiO<sub>2</sub> ON CEMENT MORTAR

---

- [21] ASTM C109/C109M-16a, *Standard Test Method for Compressive Strength of Hydraulic Cement Mortars (Using 2-in. or [50-mm] Cube Specimens)*, 2016.
  - [22] ASTM C157/C157M-17, *Standard Test Method for Length Change of Hardened Hydraulic-Cement Mortar and Concrete*, 2017.
  - [23] ASTM C1012 / C1012M – 15, *Standard Test Method for Length Change of Hydraulic-Cement Mortars Exposed to a Sulfate Solution*, 2015.
  - [24] M.S. Khalafalla, O.A. Hodhod, I.A. Adam, *Improving the Mechanical Properties of Cement Mortar By Nano Titanium*, **Journal of Engineering Sciences, Assiut University, Faculty of Engineering**, 43(5), 2015, pp. 663- 681.
  - [25] B.Y. Lee, A.R. Jayapalan, K.E. Kurtis, *Effects of nano-TiO<sub>2</sub> on properties of cement-based materials*. **Magazine of Concrete Research**, 65, 2013, pp. 1293–1302.
  - [26] R. Zhang, X. Cheng, P. Hou, Z. Ye, *Influences of Nano-TiO<sub>2</sub> on the Properties of Cement-based Materials: Hydration and Drying Shrinkage*, **Construction and Building Materials**, 81, 2015, pp. 35–41.
  - [27] P. Duan, C. Yan, W. Luo, W. Zhou, *Effects of Adding Nano-TiO<sub>2</sub> on Compressive Strength, Drying Shrinkage, Carbonation and Microstructure of Fluidized Bed Fly Ash Based Geopolymer Paste*, **Construction and Building Materials**, 106, 2016, pp. 115–125.
  - [28] M. Hasebe, H. Edahiro, *Experimental Studies on Basic Properties of Concrete Using TiO<sub>2</sub> as Admixture*, **Hokkaido University Collection of Scholarly and Academic Papers: HUSCAP**. 2013.
  - [29] M.H. Zhang, H.G. Wang, *Strength and Drying Shrinkage of Pavement Concrete with Nano Particles*, **Advanced Materials Research**, 662, 2013, pp. 182-185.
  - [30] A. Nazari, S. Riahi, *The effects of TiO<sub>2</sub> nanoparticles on properties of binary blended concrete*, **Journal of Composite Materials**, 45, 2011, pp. 1181–1188.
  - [31] A. Suleiman, M. Nehdi, *Effect of Pore Structure on Concrete Deterioration by Physical Sulfate Attack*, **Resilient Infrastructure Conference. London**, 2016, paper: (MAT-720-1)-(MAT-720-9).
  - [32] B.Y. Lee, *Effect of Titanium Dioxide Nanoparticles on Early Age and Long Term Properties of Cementitious Materials*, **PhD Thesis, School of Civil & Environmental Engineering, Georgia Institute of Technology**, 2012.
  - [33] U. Sudha, V. Vishwakarma, D. Ramachandran, R.P. George , K. Kumari, R. Preetha, U.K. Mudali, C.S. Pillai, *Nano Phase Modification of Fly Ash Concrete for Enhanced Corrosion Resistance, Durability & Antibacterial Activity in Marine Environment*. 2015, pp. 64-70. Available at:  
<https://www.masterbuilder.co.in/data/edata/Articles/November2015/64.pdf>
  - [34] F. Hamidi, F. Aslani, *TiO<sub>2</sub>-based Photocatalytic Cementitious Composites: Materials, Properties, Influential Parameters, and Assessment Techniques*. **Nanomaterials**. 9(10), 2019, 1444. <https://doi.org/10.3390/nano9101444>.
-